

Ângela A. Teixeira-Neto[#]

Departamento de Química Fundamental, Instituto de Química, Universidade de São Paulo, CP 26077, 05508-000 São Paulo - SP, Brasil

Leonardo Marchese

Dipartimento di Scienze e Tecnologie Avanzate, Università del Piemonte Orientale "A. Avogadro", Via Bellini 25G, I-15100 Alessandria, Italia

Heloise O. Pastore*

Departamento de Química Inorgânica, Instituto de Química, Universidade Estadual de Campinas, CP 6154, 13084-862 Campinas-SP, Brasil

Recebido em 13/5/08; aceito em 29/8/08; publicado na web em 5/2/09

Vanadium-containing molecular sieves are redox catalysts and are good candidates as substitutes for oxide-supported V_2O_5 in a number of reactions. These materials have the advantage of presenting better dispersion of vanadium species, as well as shape-selective properties and controllable acidities. They may be prepared by one-pot synthesis or by post-synthesis methods and a number of techniques such as diffuse reflectance UV-visible spectroscopy, ^{51}V nuclear magnetic resonance and electron paramagnetic resonance, to name but a few, have been used to characterize these materials. In this review, methods of preparation of vanadium-modified molecular sieves, their characterization and applications in catalysis are discussed.

Keywords: vanadium; oxidation catalysts; zeolites.

INTRODUCTION

The incorporation of transition metals in zeolite lattices is a research area of great interest in the catalysis field. The isomorphous substitution of metals like iron, chromium or zinc in the framework of molecular sieves has been proved and discussed.¹ Vanadium, in special, is known for its potential as a redox catalyst, particularly when homogeneously dispersed in solid supports.²

Molecular sieves containing vanadium species provide not only the desired redox properties, but the likewise structural and shape-selective properties which are characteristic of this sort of material. In the specific case of microporous crystalline materials, they have the advantage of presenting high hydrothermal stabilities, high surface areas and pore volumes and controlled acidity. On the other hand, mesoporous materials may provide good catalysts for the oxidation of aromatic molecules, which are too large to have access to catalytic sites in microporous materials.

The aim of this paper is to present a state-of-the-art review of these promising redox shape-selective catalysts, focusing on the relationship of the preparation methods with the kind of vanadium species present and their role in catalysis.

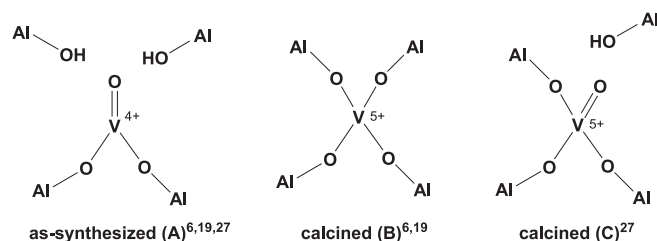
PREPARATION METHODS AND STRUCTURE OF VANADIUM SITES

One-pot synthesis

In Table 1 are listed the first occurrences of the known structures of vanadium containing molecular sieves in the literature, prepared by the introduction of the vanadium source in the synthesis gel.

The first microporous materials containing framework vanadium atoms to be synthesized were the vanadoaluminophosphates (VAPO). A patent deposited by Union Carbide in 1985³ claims the production of VAPO with **AFI** structure, VAPO-5, but this material still presented some impurities. Synthesis of pure VAPO-5 was achieved only in 1990 by Montes *et al.*⁴ The structures VAPO-11,⁵ -21,⁵ -31,⁶ -17,⁷ -41⁸ and -18⁹ were successfully prepared over the last three decades (Table 1). Recently, a mesoporous VAPO with hexagonal MCM-41-like pores was also synthesized.¹⁰

In general, as-synthesized VAPOs present V^{4+} ions occupying the positions of phosphorus atoms (Scheme 1, structure A). The calcination process leads to the total oxidation of V^{4+} to V^{5+} . This process is reversible by reduction under H_2 atmosphere. The structure of the vanadium ion in the calcined sample is not a consensus in all reports. Some authors claim that V^{5+} still bears a $V=O$ bond¹¹ (Scheme 1, structure C) while others claim that the in the majority of vanadium sites V^{5+} is bonded to four $-O-Al$ (Scheme 1, structure B).^{7,12} Typically, vanadium amounts in VAPO materials lie between 0.5 to 1%.^{7,12}



Scheme 1

Since the late 80's, vanadium ions began to be introduced in aluminosilicate structures (Table 1). The most studied microporous vanadosilicate prepared by one-pot synthesis is the vanadosilicalite VS-1, which has **MFI** structure and will be called [V]-**MFI** from now on.¹³ A very complete physico-chemical characterization of this

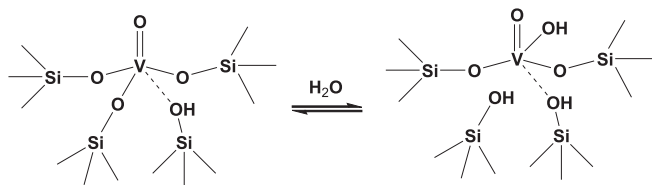
*e-mail: gpmmm@iqm.unicamp.br

[#]Endereço atual: Universidade Federal do ABC, Rua Santa Adélia, 166, 09210-170 Santo André-SP

Table 1. Vanadium-containing molecular sieves prepared by one-pot syntheses

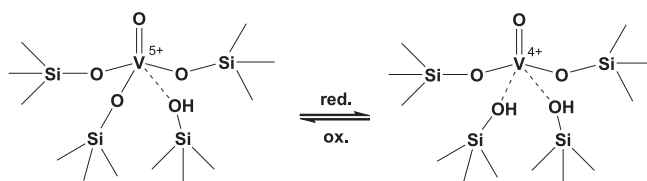
Material	V source	Year	Ref.
VAPO-5 (impure)	V ₂ O ₅	1985	3
VAPO-11	V ₂ O ₅	1985	5
VAPO-21	V ₂ O ₅	1985	5
[V]-MEL	VOSO ₄	1989	76
VAPO-5 (pure)	V ₂ O ₅	1990	12
[V]-MFI	VCl ₃	1991	13
[V]-NCL-1	VOSO ₄	1992	77
[V]-MCM-41	VOSO ₄	1994	20
[V]-ZSM-48	VOSO ₄	1994	78
[V]-MTW	VOSO ₄	1995	79
[V]-HMS	VOSO ₄	1995	22
VAPO-31	V ₂ O ₅	1996	6
[V]-MFI	VOSO ₄	1996	59
[V]-MCM-48	VOSO ₄	1996	67
[V]-beta	V ₂ O ₅	1997	80
AM-6	VOSO ₄	1997	81
[V]-FER	VOSO ₄	1999	61
VAPO-17	VOSO ₄	2000	7
[V,Al]-MCM-41	VOSO ₄	2002	23
AM-13, AM-14	VOSO ₄	2002	82
VAPO-41	V ₂ O ₅	2003	8
VAPO-18	V ₂ O ₅	2004	9
[V,Al]-MWW	VOSO ₄	2005	27
mesoporous VAPO	VOSO ₄	2005	10

material has been carried out by Centi *et al.*¹⁴ The authors used a combination of techniques, including wide-line ⁵¹V nuclear magnetic resonance (NMR), X ray photoelectron spectroscopy (XPS), electron paramagnetic resonance (EPR) and diffuse reflectance UV-visible spectroscopy (DR-UV-Vis) to propose a model of the coordination environment of tetrahedral V⁵⁺ sites in the silicalite structure (Scheme 2). Besides tetrahedral V⁵⁺, extractable V₂O₅ domains were found in the calcined sample.

**Scheme 2**

Sen *et al.*¹⁵ proposed similar structures for calcined [V]-MEL (VS-2) by combining ⁵¹V liquid state NMR and EPR data. Moreover, the authors proposed structures for vanadium environment in the gels, as-synthesized, calcined (hydrated and dehydrated), and reduced samples. The proposed mechanism for oxidation/reduction of vanadium sites in the calcined samples is illustrated in Scheme 3.

The symmetry of vanadium redox sites is also a matter of discussion. By means of cyclic voltammetry and EPR studies, Venkathathri

**Scheme 3**

*et al.*¹⁶ found that in [V]-MFI and [V]-MEL vanadium redox sites are found in distorted tetrahedral symmetry and square pyramidal symmetry, according to their location in the zeolite framework. Also, they assumed that the square pyramidal species are formed from the oxidation of V⁴⁺ ions present in the as-synthesized samples, while the distorted tetrahedral species are formed directly during the synthesis procedure. A combination of ESR, photoluminescence spectroscopy and XAFS studies, on the other hand, carried out by Anpo *et al.*¹⁷ in 2003, revealed the presence of trigonal pyramid symmetry only, with different bond angles in [V]-MFI and [V]-MEL. In this last study, only dehydrated samples were analyzed, which indicates the possibility that the square pyramidal sites found by Venkathathri *et al.* were generated by the coordination of water molecules.

It is interesting to note that most authors report that dehydrated vanadium-containing molecular sieves are white in color, while hydrated samples present a yellow color whose intensity depends on the vanadium content. This mechanism is often related to a change in coordination of V⁵⁺ from tetrahedral to octahedral, by interaction with one or two water molecules.¹⁸ In fact, ESR results indicate that, in [V]-MFI, most of the vanadium species exist on the surface of the material, where H₂O molecules are easily accessible and thus distorted octahedral VO²⁺ species can be easily generated.¹⁷

Mesoporous vanadium-containing molecular sieves are another important class of materials that have been developed during the last decades. MCM-41 was first synthesized in 1992 by Mobil researchers¹⁹ and the first time that [V]-MCM-41 appeared was in 1994 (Table 1).²⁰ It presents a hexagonal pore structure very similar to that of MCM-41 with a Si/V ratio equal to 60 and is prepared in the absence of V₂O₅ domains. Cubic [V]-MCM-48 has also been prepared,²¹ as well as the also hexagonal [V]-HMS, which is prepared using primary amines as templates.²²

A vanadoaluminosilicate with MCM-41 structure, [V,Al]-MCM-41, has been synthesized in 2002.²³ As far as we know, only few molecular sieves prepared by one-pot synthesis contained both V and Al simultaneously, such as [V,Al]-MCM-41²³ and the microporous [V,Al]-beta²⁴ and [V,Al]-MWW.²⁵ These materials present very interesting properties as bifunctional acid/redox catalysts.

Other methods

Besides one-pot syntheses, vanadium ions may be introduced in molecular sieves by post-synthesis methods. Some vanadium containing molecular sieves prepared by such methods, which include impregnation, chemical vapor deposition, between others are listed in Table 2.

A simple approach to a post-synthesis vanadium incorporation is to proceed with ion-exchange of protons or sodium ions for vanadyl cations, VO²⁺.^{26, 27} For this procedure, vanadyl sulfate is commonly used (Table 2). The difficulty in this method is that this salt hydrolyses in pH values higher than 2.8, originating V₂O₅ domains. On the other hand, low pH values lead to a competition between H⁺ and VO²⁺ ions, which may cause the incorporation of very limited vanadium amounts. To achieve higher amounts of metal incorporation, impregnation is another possibility of post-synthesis vanadium introduction,²⁸⁻³⁰ but

Table 2. Vanadium containing molecular sieves prepared by other methods

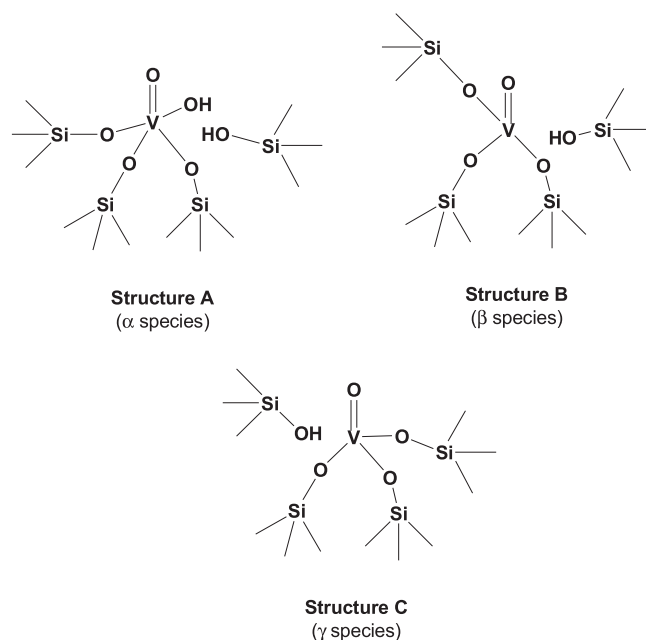
Material	Incorporation method	V source	Year	Ref.
V-MCM-48	wet impregnation	V(O-propi)	1996	83
V-BOR	wet impregnation	NH ₄ VO ₃	1996	28
V-Y	wet impregnation	VOSO ₄	1997	29
V-MCM-48	gas deposition	VO(acac) ₂	1998	84
VO-MFI, VO-MOR, VO-Y, VO-X	ion-exchange	VOSO ₄	1998	26
V-MFI	chemical vapor deposition	VOCl ₃	1998	26
V-beta	wet impregnation in dealuminated zeolite	NH ₄ VO ₃	1998	33
V-ALPO-5	wet impregnation	VOSO ₄	2000	30
V-beta, V-MFI	solid state ion-exchange	V ₂ O ₅	2004	31
V-MCM-48	ion-exchange	Na ₃ VO ₄	2005	85
VO-MWW	ion-exchange	VOSO ₄	2005	27

this method leads to V₂O₅ aggregates, which are often not interesting for catalysis. Still another approach is based on methods that do not involve contact with an aqueous solution: chemical vapor deposition (CVD), solid state ion-exchange and sublimation.^{26, 31, 32} In these methods the metallic species is vaporized at high temperatures and/or at low pressures and deposited on the material surface. The advantage is that they avoid the restricted diffusion of solvated oligomer species in aqueous exchange, which leads to poorly dispersed oxide domains at external surfaces.

A study comparing the different vanadium-modified microporous molecular sieves preparation methods was carried on by Wachs *et al.*²⁶ and revealed the presence of isolated structural vanadium species in materials prepared by one-pot synthesis and of VO²⁺ species in the materials prepared by ion-exchange (non temperature treated, pH values lower than 2.8). In materials prepared by CVD it was observed the presence of V₂O₅ aggregates in the interior of the cavities and/or on the surface of the molecular sieves, as well as VO²⁺ cations in some cases. The characterization techniques used for this study were DR-UV-Vis, EPR and XPS. According to the authors, it is possible to distinguish between extra- and intra-zeolite vanadium oxide aggregates by the use of XPS.

Dimitrova *et al.*³¹ have prepared vanadium-modified molecular sieves starting from borosilicates beta and MFI, from which the boron species were extracted and then a solid-state ion-exchange with V₂O₅ was performed. Although the authors claim that only two different VO²⁺ species were found, as counter-ions and in silanol nests, it is clear from the bands at approximately 400 nm in DR-UV-Vis spectra that V₂O₅ aggregates are present.³¹

The group of Prof. Che³³⁻⁴² performed an exhaustive work on the synthesis and characterization of vanadium-modified beta zeolite. They first prepared it on 1998, by the dealumination of zeolite beta with an acid solution and then allowing it to contact with a NH₄VO₃ aqueous solution.³³ The authors have proposed, mainly by using photoluminescence spectroscopy, three principal vanadium species in V-beta (α , β and γ), depending on the location of the atom in the zeolite lattice (Scheme 4).³⁵ This method seems thus to introduce vanadium ions as framework species, but this procedure is possible in this case only because beta-zeolite is easily dealuminated when in contact with acid solutions, which is not possible for all zeolites.

**Scheme 4**

USE IN CATALYSIS

In this section data obtained using vanadium-modified molecular sieves for catalysis until this moment will be presented. Some of the most representative data for microporous vanado(alumino)silicates, microporous vanadoaluminophosphates and mesoporous materials, as well as some studies that compare catalytic activities of microporous and mesoporous materials, will be explored.

Vanadium-modified molecular sieves are usually employed as catalysts in oxidation reactions, although many exceptions can be found. By far the most tested reaction is propane oxidative dehydrogenation (ODH) for propene production and, in some cases, the results seem very promising when compared to the traditional supported V₂O₅ catalysts.^{9, 25, 28, 43-50} The propane ODH reaction is an interesting alternative to the direct dehydrogenation, as it is an exothermic reaction:



Usually, some side products are obtained, such as carbon oxides and organic molecules such as ethene, acrolein, acrylic and acetic acid. The choice of the catalyst is thus very important in order to minimize the yield of these side products.

In general, mesoporous materials are used in reactions that comprehend bulky molecules, such as aromatics, while microporous materials are used for reacting small molecules.

Microporous materials

Vanadosilicates and vanadoaluminosilicates

As it was the first vanadium-containing molecular sieve to be synthesized and the better characterized, [V]-MFI is the most used as a catalyst. In some reactions, for instance, selective production of hydrazine by oxidation of ketone-NH₃ system by H₂O₂ it is clearly more active than its titanium analogue, [Ti]-MFI,⁵¹ but in some cases, as for reduction of NO_x⁵² it is less active. In this last case, however, the simultaneous incorporation of vanadium and titanium increase the activity of the catalyst, revealing a cooperative effect between the two metals. In the oxidation of ethylbenzene⁵³ it proved to be less active than [Sn]-MFI. In oxidation of para-chlorotoluene to para-

chlorobenzaldehyde⁵⁴ it was more active than [V]-MEL and much more active and selective than vanadium-impregnated MFI and MEL zeolites. The oxidation of aromatic molecules is an important process, as oxygenated aromatic compounds are widely used industrially.

In propane ODH, high selectivities with [V]-MFI were obtained, but only at very low conversions, such as 5%.²⁸ Using a membrane constituted by [V]-MFI, Julbe *et al.*⁴⁶ were able to achieve a maximum yield of 7% of propene and an activity much higher than that of MFI zeolite. When [V,Al]-MWW was used for propane ODH, propene yields of 5% were achieved, with reaction temperatures (350-550 °C) much lower than those used with the [V]-MFI membrane (550-650 °C).⁵⁵ It is important to note that acidity of [V,Al]-MWW may be tuned by exchange with alkaline ions, which provide mild acid sites that collaborate with vanadium sites to promote higher selectivities towards propene.

Some studies relate the vanadium species found in [V]-MFI with catalytic activity. In the transformation of ethanol, for instance, Kannan *et al.*⁵⁶ claim that only V=O species are selective for acetaldehyde while both V=O and V-O-Si species are selective for diethyl ether. This reaction is important for the production of value-added chemicals from bio-based ethanol. The study was done with the aid of NMR and ESR techniques. Also, the authors noted that intrinsic activity is 10 times larger for framework vanadium than for extra-framework species. Tetrahedrally coordinated V=O species are also responsible for the activity in the photocatalytic decomposition of NO, because they are excited to a (V⁴⁺-O)* state.⁵⁷ Its activity is much higher than that of SiO₂-supported V₂O₅.

In disagreement with the results presented in the previous cited studies, Wang *et al.*⁵⁸ stated that in the methanol oxidation reaction, for the production of formaldehyde, [V]-MFI has an activity comparable to that of SiO₂-supported V₂O₅, with similar selectivity. Also, they claim that the structure of vanadium species is similar in both catalysts and that [V]-MFI does not present any V=O bonds. The V-O-Si species are thus, according to the authors, the responsible for catalytic activity. The results presented in this work are based mostly on Raman spectra, and the conclusions differ much from all the other papers on characterization of vanadium sites in [V]-MFI.

The synthesis method is a very important factor in order to obtain lattice vanadium species. When prepared in acid media, [V]-MFI presents an activity for toluene oxidation much lower than that of the sample prepared in alkaline media.⁵⁹ The material prepared in acid media has a much higher amount of extractable extra-framework vanadium species, which are not active for the oxidation reaction. Toluene oxidation is an important reaction for the industrial production of benzaldehyde and benzoic acid.

When prepared by CVD, vanadium-containing MFI presents higher activity in ethane ODH than vanadium-impregnated MFI, with maximum dehydrogenation rate in the order of 1.10⁻³ mol s⁻¹ V⁻¹.³² High vanadium amounts inhibit the reaction, as VO_x domains are created. Also in this work the authors claim that the active species are the V=O.

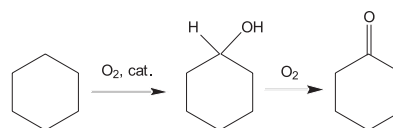
[V]-FER was used for styrene epoxidation⁶⁰ and toluene oxidation.⁶¹ In the first reaction, it showed activities and selectivities to styrene oxide and benzaldehyde, respectively, similar to the ones obtained over [Ti]-FER. For both reactions impregnated materials presented low selectivity to desired products. When vanadium species are more disperse, conversion values tend to increase.

Vanadoaluminophosphates (VAPOs)

The most studied VAPO catalyst is VAPO-5, with AFI structure. For alkene epoxidation and oxidation of aromatics, VAPO-5 presented better selectivities to the desired products as homogeneous

vanadium-containing systems and polymer-supported complexes, with comparable conversion values.⁶² Also, this catalyst did not present metal lixiviation in aqueous media. When compared to vanadium-impregnated ALPO-5 for propane ODH, VAPO-5 showed higher activities, as it presents isolated vanadium species, while ALPO-5 did not present any activity.⁶³ Okamoto *et al.*³⁰ observed that VAPO-5 catalysts prepared with more than 1% vanadium presented extraframework species that are less selective, less active and block the access to framework active sites. A method used by the authors to increase vanadium loading without creating extraframework species was to further ion-exchange VAPO-5 with vanadyl ions, raising vanadium amount from 0.38 to 0.90%. This approach increased catalytic activity of VAPO-5 in propane ODH.

For some reactions, for instance, cyclohexane oxidation, AEL structure (VAPO-11) provided better results than AFI (VAPO-5), which illustrates the importance of the structure in catalysis.⁶⁴ Cyclohexane oxidation leads to cyclohexanol and cyclohexanone and is usually catalyzed by cobalt compounds:



In this reaction cobalt and chromium containing catalysts provided better results than VAPOs, which led to deep oxidation products. The structure AEI (VAPO-18) was compared to AFI for ethane ODH, for ethene production, and it proved to be more selective.⁹ The simultaneous incorporation of cobalt facilitates vanadium incorporation and improves selectivity.

For both transformation of camphene⁶⁵ and transformation of cyclohexanol,⁶⁶ the presence of vanadium ions did not improve catalytic activity. For those specific reactions, in fact, acid sites present in SAPO catalysts were more interesting than vanadium itself.

Mesoporous materials

[V]-MCM-41 and [V]-HMS have been widely used in catalysis. [V]-MCM-48, however, is cited in a much smaller number of papers. When applied in catalysis, those materials are often compared to their titanium-containing analogues. When used in benzene hydroxylation to phenol, for instance, [V]-MCM-41 was less active than [Ti]-MCM-41, but from the metal-HMS catalysts, [V]-HMS was the most active.⁶⁷ In this reaction, selectivity to phenol achieved 100% at low conversion values (~10%).

The vanadium source is an important factor when it comes to the synthesis of [V]-MCM-41. Selvam *et al.*⁶⁸ reported that vanadium incorporation varies according to its source: tetravalent salts seem to be more efficient. For catalysis purposes, then, materials containing higher amounts of well dispersed vanadium ions, prepared from tetravalent sources, are more active. Those materials, with vanadium amounts varying from 0.2 to 1.2%, were tested on cyclohexane oxidation. When tested in the same reaction, [V]-MCM-48 presented high conversions and a minimal vanadium leaching.⁶⁹

When compared to SiO₂-supported V₂O₅ in propane selective oxidation, [V]-MCM-41 and [V]-MCM-48 containing up to 1% vanadium were much more selective.⁷⁰ Materials containing polymeric domains lead to formation of oxygenated products such as acrolein, acetaldehyde and acetic acid.

A method developed by ion-exchange of the cetyltrimethylammonium template from MCM-41 with VO(C₂O₄) and posterior calcination led to a material that showed higher efficiency in methane partial oxidation than [V]-MCM-41 prepared by one-pot synthesis.⁷¹

According to the authors, VO-exchanged MCM-41 presents weakly bonded V=O species that are more active than strongly bonded ones, generated by one-pot synthesis. For microporous materials, however, V=O species seem to have quite similar characteristics when the material is prepared whether by one-pot synthesis or by ion-exchange.²⁷

When prepared by one-pot synthesis [V]-HMS presented higher selectivity to benzaldehyde on toluene oxidation when compared to V-HMS prepared by molecular designed dispersion.⁷² The latter increases selectivity to carbon oxides.

Vanadium-containing mesoporous materials are also useful in photocatalysis. On propane photooxidation, for instance, [V]-MCM-41 presented high conversion values. The selectivity of this catalyst could be further improved when titanium ions were co-incorporated.

Microporous versus mesoporous materials

Few papers compare differences in catalytic activities of microporous and mesoporous vanadium-containing molecular sieves. In benzene hydroxylation, for instance, all [V]-MCM-41, [V]-MCM-48, [V]-MFI and [V]-beta were tested.⁷³ As benzene is a relatively bulky molecule, mesoporous materials presented higher activities, while [V]-MCM-41 was better than [V]-MCM-48.

In the oxidation of alkylsulfides [V]-MFI, [V]-MEL and [V]-HMS, were tested, together with their Ti-containing analogues.⁷⁴ In this case, vanadosilicates presented higher conversions than titanosilicates. Activity remained in the order [V]-HMS > [V]-MEL > [V]-MFI. Also in this case, pore diameter plays an important role in catalytic activity.

V-USY and V-Y prepared by impregnation were tested n-butane dehydrogenation.⁷⁵ An O₂-free atmosphere was used. V-USY showed both higher activity and selectivity, due to its higher vanadium loading and milder acidity. Both catalysts were more active than Al₂O₃-supported V₂O₅.

CONCLUSIONS

Vanadium-containing molecular sieves are important oxidation catalysts that are beginning to gain notoriety in the last years. It was shown in this review that a large number of this kind of catalysts have been, and continue to be, prepared, characterized and applied in catalytic reactions. It was observed that, in general, the most selective catalysts are the ones that present better dispersed and homogeneous vanadium species. Oxide clusters lead to deep oxidation products and often block access to the molecular sieves pores and/or cavities. Catalysts prepared by one-pot synthesis are still the ones that best fulfill the compromise between vanadium concentration and metal dispersion. Most of the reviewed papers present materials with vanadium concentrations that go up to 1%. The choice of the structure should depend on the reaction, as large molecules require mesoporous catalysts, while small molecules may benefit from the shape selectivity of microporous materials. For some applications, the incorporation of a second metal, as titanium, for instance, may lead to a cooperative effect between the two metals and good results can be obtained.

REFERENCES

- Pastore, H. O.; *Quim. Nova* **1996**, *19*, 372.
- Weckhuysen, B. M.; Keller, D. E.; *Catal. Today* **2003**, *78*, 25.
- Flanigen, E. M.; Lok, B. M. T.; Patton, R. L.; Wilson, S. T.; *US pat.* **158976**, **1985**.
- Montes, C.; Davis, M. E.; Murray, B.; Narayana, M.; *J. Phys. Chem.* **1990**, *94*, 6431.
- Pyke, D. R.; Whitney, P.; Houghton, H.; *Appl. Catal.* **1985**, *18*, 173.
- Venkatathri, N.; Hegde, S. G.; Sivasanker, S.; *J. Chem. Soc., Chem. Commun.* **1995**, 151.
- Zahedi-Niaki, M. H.; Zaidi, S. M. J.; Kaliaguine, S.; *Appl. Catal., A* **2000**, *196*, 9.
- Venkatathri, N.; *Appl. Catal., A* **2003**, *242*, 393.
- Concepcion, P.; Blasco, T.; Nieto, J. M. L.; Vidal-Moya, A.; Martinez-Arias, A.; *Microporous Mesoporous Mater.* **2004**, *67*, 215.
- Venkatathri, N.; Srivastava, R.; *Catal. Commun.* **2005**, *6*, 177.
- Prakash, A. M.; Kevan, L.; *J. Phys. Chem. B* **1999**, *103*, 2214.
- Montes, C.; Davis, M. E.; Murray, B.; Narayana, M.; *J. Phys. Chem.* **1990**, *94*, 6431.
- Rigutto, M. S.; Vanbekkum, H.; *Appl. Catal.* **1991**, *68*, L1.
- Centi, G.; Perathoner, S.; Trifiro, F.; Aboukais, A.; Aissi, C. F.; Guelton, M.; *J. Phys. Chem.* **1992**, *96*, 2617.
- Sen, T.; Ramaswamy, V.; Ganapathy, S.; Rajamohanam, P. R.; Sivasanker, S.; *J. Phys. Chem.* **1996**, *100*, 3809.
- Venkatathri, N.; Vinod, M. P.; Vijayamohanam, K.; Sivasanker, S.; *J. Chem. Soc. Chem. Commun.* **1996**, *92*, 473.
- Anpo, M.; Higashimoto, S.; Matsuoka, M.; Zhanpeisov, N.; Shioya, Y.; Dzwigaj, S.; Che, M.; *Catal. Today* **2003**, *86*, 287.
- Prakash, A. M.; Kevan, L.; *J. Phys. Chem. B* **2000**, *104*, 6860.
- Kresge, C. T.; Leonowicz, M. E.; Roth, W. J.; Vartuli, J. C.; Beck, J. S.; *Nature* **1992**, *359*, 710.
- Reddy, K. M.; Moudrakovski, I.; Sayari, A.; *J. Chem. Soc. Chem. Commun.* **1994**, 1059.
- Zhang, W. Z.; Pinnavaia, T. J.; *Catal. Lett.* **1996**, *38*, 261.
- Reddy, J. S.; Sayari, A.; *J. Chem. Soc. Chem. Commun.* **1995**, 2231.
- Lee, D. S.; Liu, T. K.; *J. Sol-Gel Sci. Technol.* **2002**, *23*, 15.
- Gunduz, G.; Dimitrova, R.; Yilmaz, S.; Dimitrov, L.; *Appl. Catal., A* **2005**, *282*, 61.
- Albuquerque, A.; Marchese, L.; Lisi, L.; Pastore, H. O.; *J. Catal.* **2006**, *241*, 367.
- Wark, M.; Koch, M.; Bruckner, A.; Grunert, W.; *J. Chem. Soc. Chem. Commun.* **1998**, *94*, 2033.
- Albuquerque, A.; Pastore, H. O.; Marchese, L.; *Stud. Surf. Sci. Catal.* **2005**, *158*, 901.
- Centi, G.; Trifiro, F.; *Appl. Catal., A* **1996**, *143*, 3.
- Trujillo, C. A.; Uribe, U. N.; Knops Gerrits, P. P.; Oviedo, L. A.; Jacobs, P. A.; *J. Catal.* **1997**, *168*, 1.
- Okamoto, M.; Luo, L.; Labinger, J. A.; Davis, M. E.; *J. Catal.* **2000**, *192*, 128.
- Dimitrova, R.; Neinska, Y.; Mihalyi, M.; Pal-Borbely, G.; Spassova, M.; *Appl. Catal., A* **2004**, *266*, 123.
- Lacheen, H. S.; Iglesia, E.; *J. Phys. Chem. B* **2006**, *110*, 5462.
- Dzwigaj, S.; Peltre, M. J.; Massiani, P.; Davidson, A.; Che, M.; Sen, T.; Sivasanker, S.; *Chem. Commun.* **1998**, 87.
- Dzwigaj, S.; Matsuoka, M.; Franck, R.; Anpo, M.; Che, M.; *J. Phys. Chem. B* **1998**, *102*, 6309.
- Dzwigaj, S.; Matsuoka, M.; Anpo, M.; Che, M.; *J. Phys. Chem. B* **2000**, *104*, 6012.
- Dzwigaj, S.; El Malki, E. M.; Peltre, M. J.; Massiani, P.; Davidson, A.; Che, M.; *Top. Catal.* **2000**, *11*, 379.
- Dzwigaj, S.; Massiani, P.; Davidson, A.; Che, M.; *J. Mol. Catal., A* **2000**, *155*, 169.
- Dzwigaj, S.; Matsuoka, M.; Anpo, M.; Che, M.; *Catal. Lett.* **2001**, *72*, 211.
- Dzwigaj, S.; Che, M.; *J. Phys. Chem. B* **2005**, *109*, 22167.
- Ivanova, E.; Hadjiivanov, K.; Dzwigaj, S.; Che, M.; *Microporous Mesoporous Mater.* **2006**, *89*, 69.
- Gora-Marek, K.; Datka, J.; Dzwigaj, S.; Che, M.; *J. Phys. Chem. B* **2006**, *110*, 6763.

42. Dzwigaj, S.; Matsuoka, M.; Anpo, M.; Che, M.; *Microporous Mesoporous Mater.* **2006**, *93*, 248.
43. Concepcion, P.; Lopez Nieto, J. M.; Perez Pariente, J.; *Catal. Lett.* **1993**, *19*, 333.
44. Concepcion, P.; Nieto, J. M. L.; Perez Pariente, J.; *J. Mol. Catal., A* **1995**, *97*, 173.
45. Blasco, T.; Concepcion, P.; Nieto, J. M. L.; Perez Pariente, J.; *J. Catal.* **1995**, *152*, 1.
46. Julbe, A.; Farrusseng, D.; Jalibert, J. C.; Mirodatos, C.; Guizard, C.; *Catal. Today* **2000**, *56*, 199.
47. Santamaria-Gonzalez, J.; Luque-Zambrana, J.; Merida-Robles, J.; Maireles-Torres, P.; Rodriguez-Castellon, E.; Jimenez-Lopez, A.; *Catal. Lett.* **2000**, *68*, 67.
48. Zhou, R.; Cao, Y.; Yan, S. R.; Deng, J. F.; Liao, Y. Y.; Hong, B. F.; *Catal. Lett.* **2001**, *75*, 107.
49. Wang, Y.; Zhang, Q. H.; Ohishi, Y.; Shishido, T.; Takehira, K.; *Catal. Lett.* **2001**, *72*, 215.
50. Dzwigaj, S.; Gressel, I.; Grzybowska, B.; Samson, K.; *Catal. Today* **2006**, *114*, 237.
51. Kapoor, M. P.; Gallot, J. E.; Raj, A.; Kaliaguine, S.; *J. Chem. Soc. Chem. Commun.* **1995**, 2281.
52. Raj, A.; Roberge, D.; Kaliaguine, S.; Iwamoto, S.; Inui, T.; *Chem. Commun.* **1996**, 531.
53. Mal, N. K.; Ramaswamy, A. V.; *Appl. Catal., A* **1996**, *143*, 75.
54. Singh, A. P.; Selvam, T.; *Appl. Catal., A* **1996**, *143*, 111.
55. Teixeira-Neto, A. A.; Marchese, L.; Landi, G.; Lisi, L.; Pastore, H. O.; *Catal. Today* **2008**, *133*, 1.
56. Kannan, S.; Sen, T.; Sivasanker, S.; *J. Catal.* **1997**, *170*, 304.
57. Higashimoto, S.; Matsuoka, M.; Zhang, S. G.; Yamashita, H.; Kitao, O.; Hidaka, H.; Anpo, M.; *Microporous Mesoporous Mater.* **2001**, *48*, 329.
58. Wang, C. B.; Deo, G.; Wachs, I. E.; *J. Catal.* **1998**, *178*, 640.
59. Sen, T.; Rajamohanan, P. R.; Ganapathy, S.; Sivasanker, S.; *J. Catal.* **1996**, *163*, 354.
60. Anand, R.; Shevade, S. S.; Ahedi, R. K.; Mirajkar, S. P.; Rao, B. S.; *Catal. Lett.* **1999**, *62*, 209.
61. Shevade, S. S.; Rao, B. S.; *J. Mater. Chem.* **1999**, *9*, 2459.
62. Rigutto, M. S.; van Bekkum, H.; *J. Mol. Catal.* **1993**, *81*, 77.
63. Concepcion, P.; Lopez Nieto, J. M.; Perez-Pariente, J.; *J. Mol. Catal., A* **1995**, *97*, 173.
64. Tian, P.; Liu, Z. M.; Wu, Z. B.; Xu, L.; He, Y. L.; *Catal. Today* **2004**, *93-95*, 735.
65. Elangovan, S. P.; Arabindoo, B.; Krishnasamy, V.; Murugesan, V.; *J. Chem. Soc., Faraday Trans.* **1995**, *91*, 4471.
66. Elangovan, S. P.; Murugesan, V.; *J. Mol. Catal. A* **1997**, *118*, 301.
67. Zhang, W. Z.; Wang, J. L.; Tanev, P. T.; Pinnavaia, T. J.; *Chem. Commun.* **1996**, 979.
68. Selvam, P.; Dapurkar, S. E.; *J. Catal.* **2005**, *229*, 64.
69. Selvam, P.; Dapurkar, S. E.; *Appl. Catal., A* **2004**, *276*, 257.
70. Pena, M. L.; Dejoz, A.; Fornes, V.; Rey, E.; Vazquez, M. I.; Nieto, J. M. L.; *Appl. Catal., A* **2001**, *209*, 155.
71. Zhang, Q. H.; Yang, W.; Wang, X. X.; Wang, Y.; Shishido, T.; Takehira, K.; *Microporous Mesoporous Mater.* **2005**, *77*, 223.
72. Williams, T.; Beltramini, J.; Lu, G. Q.; *Microporous Mesoporous Mater.* **2006**, *88*, 91.
73. Lee, C. W.; Lee, W. J.; Park, Y. K.; Park, S. E.; *Catal. Today* **2000**, *61*, 137.
74. Shiraiishi, Y.; Naito, T.; Hirai, T.; *Ind. Eng. Chem. Res.* **2003**, *42*, 6034.
75. Volpe, M.; Tonetto, G.; de Lasa, H.; *Appl. Catal., A* **2004**, *272*, 69.
76. Habersberger, K.; Jiru, P.; Tvaruzkova, Z.; Centi, G.; Trifiro, F.; *React. Kinet. Catal. Lett.* **1989**, *39*, 95.
77. Reddy, K. R.; Ramaswamy, A. V.; Ratnasamy, P.; *J. Chem. Soc. Chem. Commun.* **1992**, 1613.
78. Tuel, A.; Bentaarit, Y.; *Zeolites* **1994**, *14*, 18.
79. Bhaumik, A.; Dongare, M. K.; Kumar, R.; *Microporous Mater.* **1995**, *5*, 173.
80. Chien, S. H.; Ho, J. C.; Mon, S. S.; *Zeolites* **1997**, *18*, 182.
81. Rocha, J.; Brandao, P.; Lin, Z.; Anderson, M. W.; Alfredsson, V.; Terasaki, O.; *Angew. Chem., Int. Ed.* **1997**, *36*, 100.
82. Brandao, P.; Philippou, A.; Hanif, N.; Ribeiro-Claro, P.; Ferreira, A.; Anderson, M. W.; Rocha, J.; *Chem. Mater.* **2002**, *14*, 1053.
83. Morey, M.; Davidson, A.; Eckert, H.; Stucky, G.; *Chem. Mater.* **1996**, *8*, 486.
84. Van Der Voort, P.; Morey, M.; Stucky, G. D.; Mathieu, M.; Vansant, E. F.; *J. Phys. Chem. B* **1998**, *102*, 585.
85. Gomez, S.; Garces, L. J.; Villegas, J.; Ghosh, R.; Giraldo, O.; Suib, S. L.; *J. Catal.* **2005**, *233*, 478.